

United States Department of the Interior  
Geological Survey

**The U. S. Geological Survey Coal Quality Data Base  
(COALQUAL)**

by

Robert B. Finkelman, Charles L. Oman, Linda J. Bragg,  
and Susan J. Tewalt

Open-File Report 94-177  
1994

This report is preliminary and has not been  
edited or reviewed for conformity with U.S.  
Geological Survey standards and nomenclature.

## Table of Contents

	Page
Introduction .....	1
What is the USGS Coal Quality Data Base? .....	2
Sample Collection and Analytical Protocol .....	3
Magnitude of the Coal Quality Data base .....	4
Vertical and Lateral Distribution of Coal Quality Components .....	5
Modes of Occurrence of Trace Elements .....	7
Statistical Correlations Among Coal Quality Parameters ..	8
Methods of Data Dissemination .....	10
References .....	12
Appendix .....	12

### Figures

1. Flow diagram of analytical procedures used through Sept. 1990.
2. Flow diagram of analytical procedures used after Sept. 1990.
3. Distribution of analyses in the U.S. Geological Survey Coal Quality (COALQUAL) data base.

### Tables

1. Samples in COALQUAL data base from coal-bearing areas.
2. Samples in COALQUAL data base from coal-bearing states.
3. Variation of potential air toxics among coal basins.
4. Variation of potential air toxics among coal beds in the Appalachian basin.
5. Lateral distribution of potential air toxics within the Pittsburgh coal bed from Ohio, Pennsylvania, and West Virginia.
6. Variations of potential air toxics from the top to the bottom of a set of bench samples from the Pittsburgh coal bed in Ohio.
7. Strengths and weaknesses of the USGS Coal Quality data base and cautions for its use.

## Introduction

During the energy crisis of the mid-1970s the U.S. Geological Survey (USGS), in cooperation with State Geological Survey's, initiated an ambitious project to create a comprehensive national coal information data base. This data base, known as the National Coal Resources Data System (NCRDS), was to contain information on the quantity and quality of our domestic coal resources.

In the mid-1970s energy independence, synfuels, and in-situ gasification were the hopes for the future. The NCRDS was conceived as an exploration tool to help achieve these aspirations. A major objective was to locate, measure, and characterize all of the Nation's coal resources, without regard to bed thickness, depth, location, or quality. An initial goal of the project was to obtain and characterize at least one sample per coal bed. from every geographic quadrangle (approximately 50 sq. miles) underlain by coal.

During the nearly 20 years since its inception the NCRDS's Coal Quality data base has developed into the largest publicly available data base of its kind. The data were used primarily by state Geological Surveys, university researchers, and other federal agencies. Recent legislation has stimulated new and broader interest in the Coal Quality data base. The 1990 Amendments to the Clean Air Act (U.S. Statutes, 1990) cite more than a dozen elements as potential hazardous air pollutants. The Act requires the EPA to conduct a study of the toxic air emissions from coal burning utilities. The Act also requires the EPA to perform a health risk assessment and to recommend new air toxic

regulations, if necessary, to protect human health and the environment.

Many of the new users (utilities, coal mining companies, coal industry consultants, environmentalists, state and federal agencies, etc.) of the USGS Coal Quality data base have asked questions about its history, composition, and structure. This report is intended to answer the most common questions and to help orient new users of the Coal Quality data base.

### What is the USGS's Coal Quality Data Base?

The USGS Coal Quality data base is an interactive, computerized component of the NCRDS. It contains comprehensive analyses of more than 13,000 samples of coal and associated rocks from every major coal-bearing basin and coal bed in the U. S.

The data in the coal quality data base represent analyses of the coal **as it exists in the ground**. The data commonly are presented on an as-received whole-coal basis. Other reporting bases, for example, as-analyzed, dry, ash, mineral-matter-free may be obtained on request.

A data base with nearly 2,000,000 entries is bound to contain some errors. To minimize these errors there has been a concerted effort, during the past three years, to "verify" the data in the Coal Quality data base. Every entry is being checked and rechecked against the original data (field notes, analytical reports, etc.). When possible, the sample collector is asked to verify the geology and location information. If the collector is unavailable for verification, original field notes are consulted. The verification process should be completed in 1995.

An international analog to the domestic data base is being formed. The international data base will contain coal quality information on coal from foreign countries.

### Sample Collection and Analytical Protocol

The recommended procedures for collecting samples for analysis and inclusion in the USGS Coal Quality data base are described by Stanton (1989). Detailed information on the geographic location (state, county, longitude and latitude, mine, etc.) and geologic and stratigraphic information (thickness, depth, geologic age, formation, member, bed, etc.) is recorded for each sample.

Coal and associated rock samples are analyzed by the USGS for the concentrations of approximately 75 major-, minor-, and trace-elements, and for the standard coal characteristics by the U.S. Bureau of Mines and contract laboratories using American Society of Testing and Materials standards (ASTM, 1993). The standard coal characteristics include proximate and ultimate analysis, heat content, forms of sulfur, ash-fusion temperatures, free-swelling index, and air-drying loss. Equilibrium moisture, apparent specific gravity, and hardgrove grindability are determined on selected samples. A total of 136 parameters are determined for each sample. The Appendix contains a description of all 136 parameters.

The USGS sample numbers beginning with 'D' were analyzed using a scheme described by Swanson and Huffman (1976). The sample numbers beginning with 'W' were analyzed according to the

flow chart in Figure 1. Details of the analytical procedures can be found in Golightly and Simon (1989).

A new analytical scheme for the major-, minor-, and trace-elements has been developed for both 'D' and 'W' samples analyzed after 1990. A flow chart of this scheme appears in Figure 2.

### Magnitude of Coal Quality Data Base

The samples collected or submitted for analysis and inclusion in the Coal Quality data base consist primarily of full bed core and channel samples. Some of the bed samples are collected in benches. Analyses of bench samples that need to be composited are weighted by thickness to obtain a calculated analysis of the full coal bed. Where feasible, clastic rocks (partings, overburden, underburden) associated with the coal bed are collected and analyzed. The data base also contains a small number of grab samples, density splits, and other miscellaneous samples; the sample type is recorded for all samples in the data base. Table 1 indicates the total number of samples prior to compositing bench samples and the number of samples after compositing bench samples for major coal-bearing areas. Table 2 contains information on the total number of samples, the number of samples after compositing, the number of channel samples, core samples, and miscellaneous samples for each coal-bearing state. Figure 3 illustrates the domestic distribution of analyses in the Coal Quality data base.

Finkelman and others (1991) compiled a bibliography of publications containing element data from the Coal Quality data base. The report includes a compilation of the number of analyzed

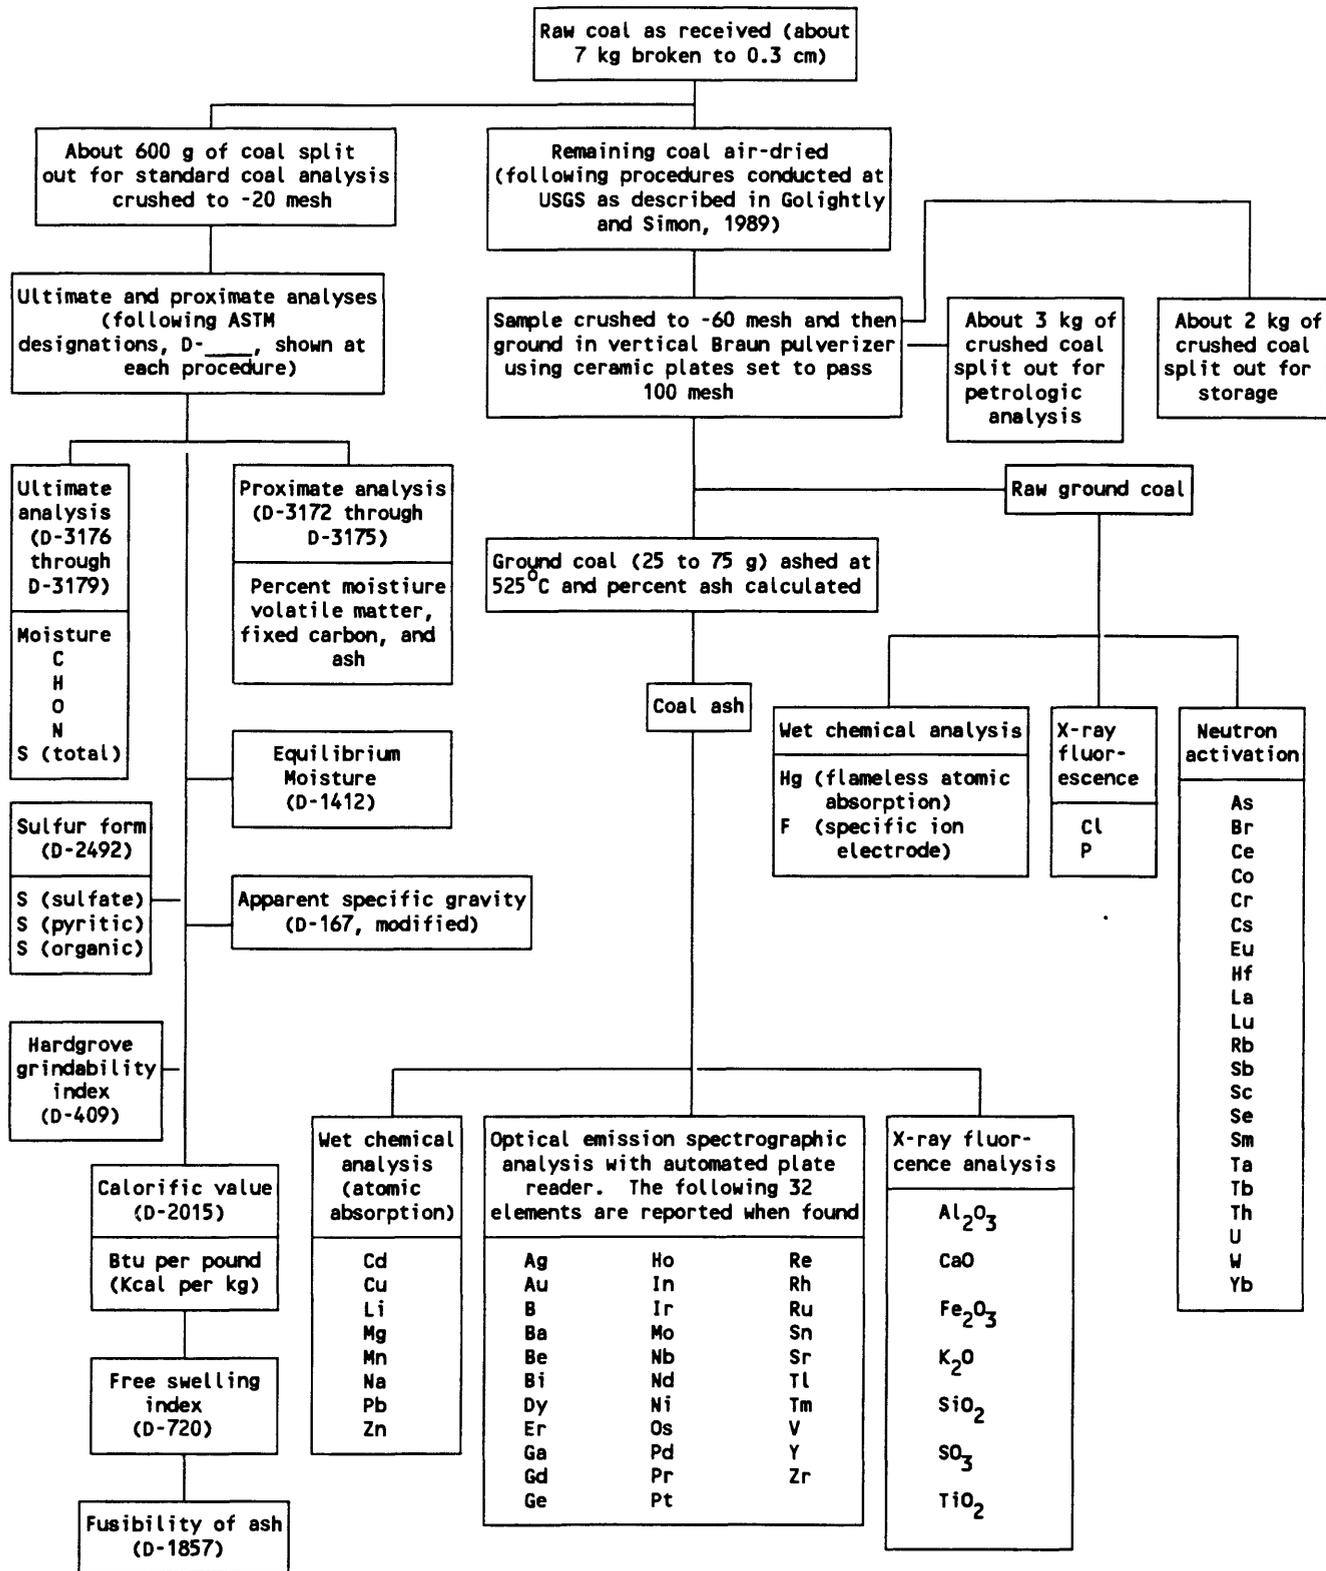


Figure 1. Flow diagram of procedures used through September 1990, for the analysis of coal samples collected. (ASTM-American Society for Testing and Materials, USGS-United States Geological Survey.)

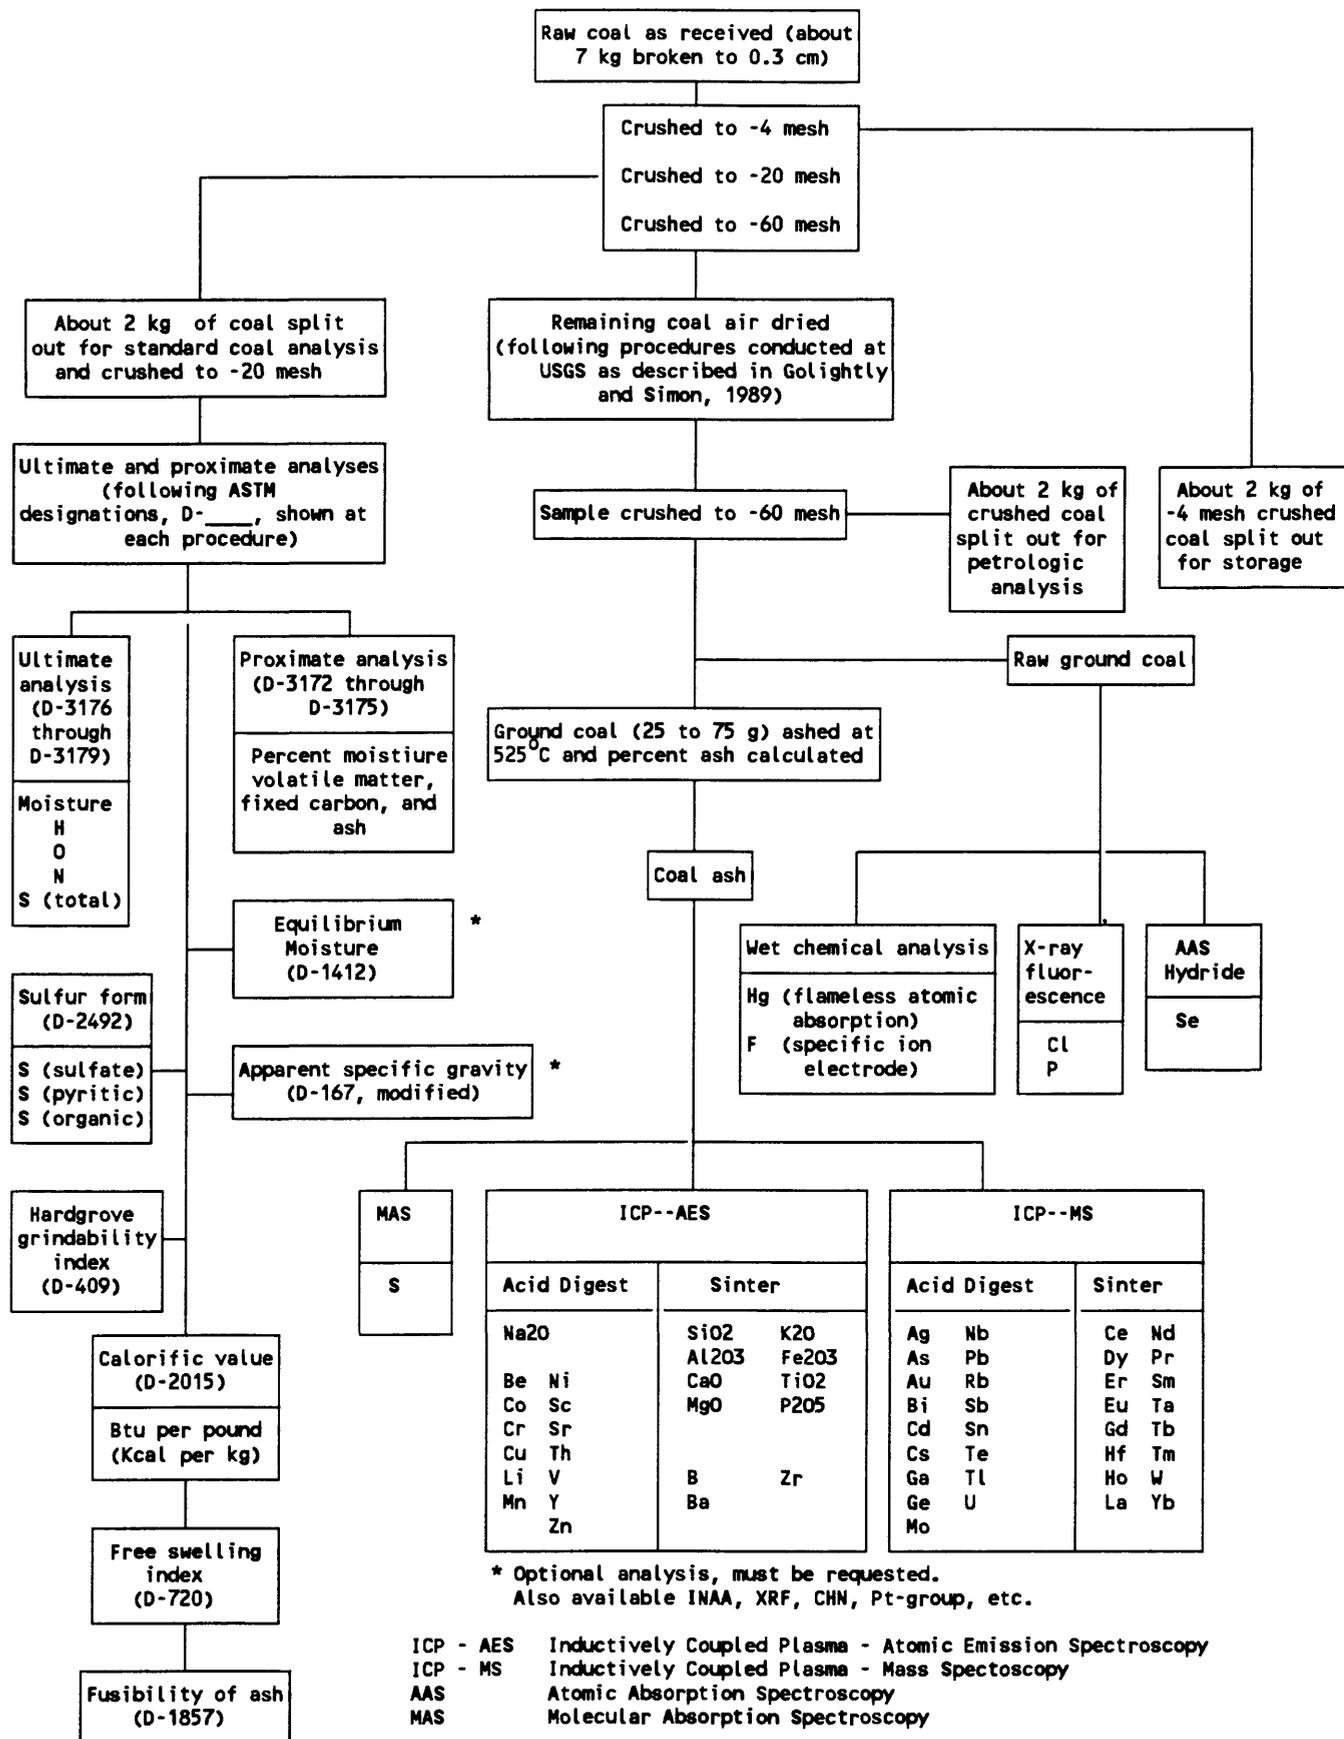


Figure 2. Flow diagram of procedures used after September 1990 for the analysis of coal samples collected. (ASTM-American Society for Testing and Materials, USGS-United States Geological Survey.)

Table 2. Samples in COALQUAL data base from coal-bearing states.

State	Total Number of Samples	Total Number of Bench Samples	Total Number of Coal Composited Bench Samples	Total Number of Coal Samples After Compositing	Total Number of Channel Samples After Compositing	Total Number of Coal Drill Core Samples After Compositing	Total Number of Rocks and Miscellaneous Samples removed from raw data base to create COALQUAL data base
ALABAMA	1032	1	-	951	503	448	80
ALASKA	672	466	75	166	145	21	115
ARIZONA	40	27	9	11	11	-	11
ARKANSAS	107	6	-	76	30	46	25
CALIFORNIA	1	-	-	-	-	-	-
COLORADO	952	361	69	372	100	272	288
GEORGIA	39	-	-	37	37	-	2
IDAHO	58	3	-	3	1	2	52
ILLINOIS	133	91	16	16	16	-	42
INDIANA	378	40	16	157	157	-	197
IOWA	145	-	-	118	33	85	27
KANSAS	45	5	1	30	30	-	11
KENTUCKY	1226	57	22	905	712	193	286
LOUISIANA	1	-	-	1	1	-	-
MARYLAND	75	15	4	59	59	-	5
MASSACHUSETTS	12	2	-	4	-	4	6
MICHIGAN	10	-	-	3	3	-	7
MISSISSIPPI	31	14	2	9	7	2	10
MISSOURI	138	41	20	91	78	13	26
MONTANA	893	483	126	360	61	299	176
NEBRASKA	17	-	-	6	6	-	11
NEVADA	14	1	-	2	2	-	11
NEW MEXICO	343	73	19	191	54	137	98
NORTH CAROLINA	55	-	-	-	-	-	55
NORTH DAKOTA	273	41	15	205	33	172	42
OHIO	805	211	75	660	468	192	9
OKLAHOMA	85	47	19	56	45	11	1
PENNSYLVANIA	1593	645	184	809	615	194	323
RHODE ISLAND	11	-	-	9	-	9	2
TENNESSEE	62	-	-	58	58	-	4
TEXAS	128	39	12	73	28	45	28
UTAH	486	176	15	173	55	118	152
VIRGINIA	585	72	30	493	414	79	50
WASHINGTON	80	43	1	14	14	-	24
WEST VIRGINIA	887	192	51	617	594	23	129
WYOMING	<u>1623</u>	<u>584</u>	<u>125</u>	<u>697</u>	<u>183</u>	<u>514</u>	<u>467</u>
	13035	3737	906	7432	4553	2879	2772

\* Full bed samples in COALQUAL data base.

Table 1. Samples in COALQUAL data base from coal-bearing areas.

Province*	Region**	Total Number of Samples	Total Number of Samples After Compositing
ALASKA	ALASKA PENINSULA	13	8
	CENTRAL ALASKA	259	49
	COOK INLET-SUSITNA	98	30
	NORTHERN ALASKA	296	78
	SEWARD PENINSULA	6	1
EASTERN	ATLANTIC COAST	67	2
	CENTRAL APPALACHIAN	2198	1777
	NORTHERN APPALACHIAN	2627	1636
	PENNSYLVANIA ANTHRACITE	72	52
	RHODE ISLAND META-ANTHRACITE	18	12
	SOUTHERN APPALACHIAN	1062	987
GULF	MISSISSIPPI	67	23
	TEXAS	197	118
INTERIOR	EASTERN	826	298
	NORTHERN	10	3
	WESTERN	445	329
NORTHERN GREAT PLAINS	FORT UNION	414	300
	NORTH CENTRAL	12	7
	POWDER RIVER	1666	612
ROCKY MOUNTAIN	DENVER	123	42
	GREEN RIVER	1117	416
	HAMS FORK	47	29
	RATON MESA	96	40
	SAN JUAN RIVER	337	193
	SOUTHWESTERN UTAH	63	42
	TERTIARY LAKE BEDS	12	7
	UINTA	614	253
WIND RIVER	44	42	
NO DATA ENTERED	NO DATA ENTERED	229	46
TOTAL SAMPLES		13,035	7,432

\* SOURCE: Cargill and others, 1976, pages 8 and 13.

\*\* SOURCE: Cargill and others, 1976, pages 9 and 13.

# NCRDS Chemical Data

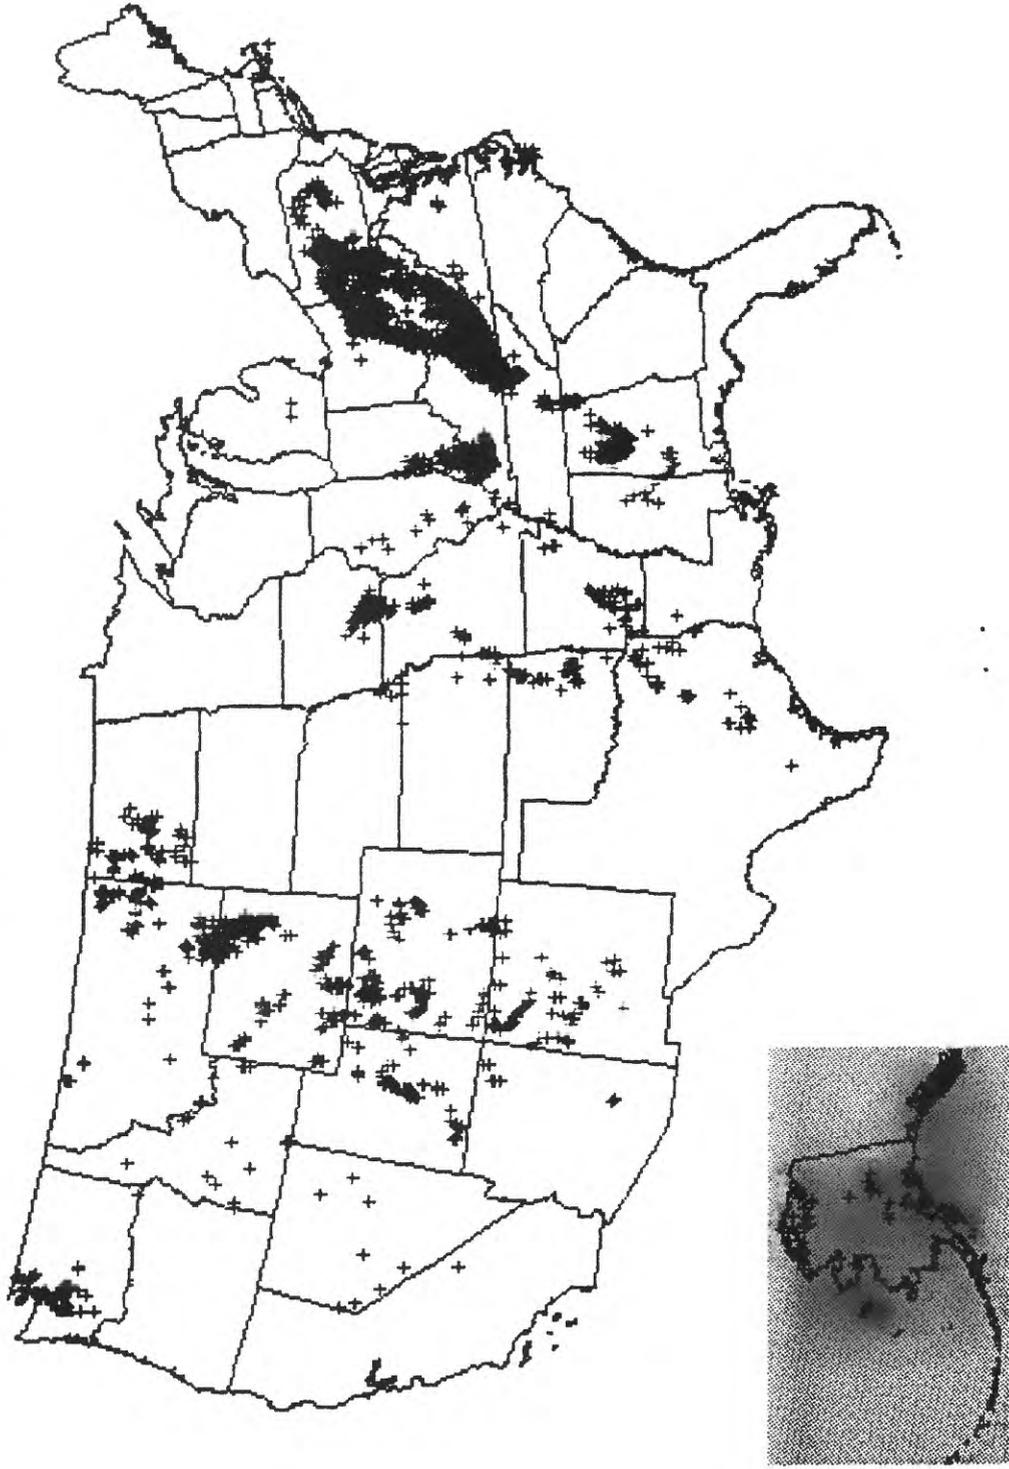


Figure 3. Distribution of analyses in the U.S. Geological Survey Coal Quality data base.

samples for each state and the number of those analyses that have been published. Approximately one-half of the data in the Coal Quality data base has been reported in publications.

Additions to the Coal Quality data base continue at a reduced level; during the past 5 years approximately 100 analyses have been added annually. The Coal Quality data base is being enhanced by merging it with coal quality data from the Illinois Geological Survey (approximately 700 analyses) and data from the New Mexico Bureau of Mines and Geology (approximately 350 analyses).

Much of the data in the data base was obtained prior to 1982. Consequently, many of the coal samples are from areas that are now mined out or where coal mining subsequently has ceased. The inclusion of these 'dated' samples does not present a problem, however, in using data from the data base for regional projections of coal quality variation.

### Vertical and Lateral Distribution of Coal Quality Components

One of the more common uses of the USGS Coal Quality data is to evaluate vertical and lateral distribution of coal quality parameters. Table 3 contains arithmetic means for the potential hazardous air pollutants (U.S. Statutes, 1990) in several coal basins. It is apparent that several elements exhibit a wide range of concentrations among the coal basins. For example, cadmium ranges from 0.1 ppm in the Appalachian basin to 4.2 ppm in the Interior Coal Province (a 4,100 percent variation:

$((4.2-.1)/.1)*100$ ). In contrast, mercury ranges from 0.12 ppm in the Powder River basin to 0.22 ppm in the Gulf Coast Province; a variation of 83 percent.

Table 4 contains arithmetic means of the potential hazardous air pollutants in six coal beds within the Appalachian basin. Some elements show a greater variation within the coal basin than among coal basins. For example, mercury has a 183 percent variation among these Appalachian basin samples, and antimony has a 318 percent variation among these samples but only a 163 percent variation among the coal basins in Table 3.

Table 5 contains arithmetic means for the potential air pollutants in six coal samples from the Pittsburgh coal bed from Ohio, Pennsylvania, and West Virginia. In this sample suite arsenic exhibits a 686 percent variation and beryllium has a 397 percent variation; larger variations than exhibited in Tables 3 or 4.

Finally, at bench scale, the smallest sampling scale in the data base, Table 6 shows substantial trace element variations among bench samples from the Pittsburgh coal bed. For example, arsenic shows a 551 percent variation among the bench samples, beryllium a 426 percent variation, cobalt a 608 percent variation, and chromium a 374 percent variation. Mercury exhibits a 480 percent variation among the bench samples; this is almost 6 times larger than its variation among the coal basins (Table 3).

Because trace element variations are as great within beds as they are within and among basins, selective mining may be an option for reducing the concentration of some trace elements in the mined coal. It should be emphasized that the USGS coal

Table 3. Comparison of potential air toxics among coal basins. (Values are arithmetic means in parts-per-million on a whole-coal basis, except for number of samples.)

	Appalachian basin	Interior Province	Gulf Coast lignites	Fort Union lignites	Powder River basin
<u>Element</u>					
Antimony	1.4	1.5	1.0	0.69	0.57
Arsenic	35.0	20.0	10.0	11.0	5.6
Beryllium	2.5	2.4	2.4	1.0	0.84
Cadmium	0.1	4.2	0.55	0.16	0.16
Chromium	17.0	19.0	24.0	6.4	8.5
Cobalt	7.2	10.0	7.2	2.4	2.3
Lead	8.4	40.0	21.0	4.8	5.5
Manganese	29.0	78.0	150.0	83.0	63.0
Mercury	0.21	0.15	0.22	0.14	0.12
Nickel	17.0	27.0	13.0	4.1	6.4
Selenium	3.5	3.2	5.7	0.82	1.1
Uranium	1.7	3.1	23.0	1.8	1.6
<u>Number of Samples</u>	4700	800	200	350	800

Table 4. Comparisons of potential air toxics among coal beds in the Appalachian basin. (Values are arithmetic means in parts-per-million on a whole coal basis, except for number of samples.)

	Meigs Creek coal bed	Redstone coal bed	Pittsburgh coal bed	Lower Freeport coal bed	Lower Kittanning coal bed	Sewell coal bed
<u>Element</u>						
Antimony	0.3	0.7	0.6	1.2	0.9	1.1
Arsenic	6.7	29.1	20.4	37.3	25.2	11.1
Beryllium	1.4	1.6	1.4	2.7	2.6	2.2
Cadmium	0.08	0.07	0.11	0.11	0.14	0.10
Chromium	16.4	13.8	14.7	17.4	16.8	11.8
Cobalt	3.2	3.5	4.6	7.6	6.7	8.0
Lead	5.3	4.0	4.9	10.4	10.6	5.5
Manganese	30.8	46.3	31.9	42.8	27.2	18.5
Mercury	0.12	0.22	0.18	0.34	0.24	0.16
Nickel	9.5	9.5	10.7	20.4	20.5	18.9
Selenium	2.9	2.4	1.9	5.0	4.3	2.4
Uranium	1.8	1.7	1.1	1.7	1.8	1.4
<u>Number of Samples</u>	54	80	194	119	219	73

Table 5. Lateral distribution of potential air toxics within the Pittsburgh coal bed from Ohio, Pennsylvania, and West Virginia. (Values are arithmetic means in parts-per-million on a whole coal basis.)

Sample	1	2	3	4	5	6
<u>Element</u>						
Antimony	0.4	1.4	0.4	0.4	1.4	0.3
Arsenic	13.3	75.1	15.0	9.6	79.8	10.0
Beryllium	1.1	1.2	1.6	1.4	1.0	0.3
Cadmium	0.10	0.07	0.14	0.06	0.09	0.04
Chromium	14.4	9.3	10.1	10.3	9.2	10.2
Cobalt	2.8	3.1	11.8	2.7	4.9	1.7
Lead	3.6	3.7	1.5	3.8	6.9	1.0
Manganese	17.8	19.1	55.1	19.7	25.6	25.3
Mercury	0.10	0.22	0.60	0.16	0.28	0.22
Nickel	7.1	6.3	20.9	9.0	9.5	4.3
Selenium	1.5	3.4	3.0	0.9	1.7	1.0
Uranium	0.8	0.3	2.0	0.9	1.4	2.4

Table 6. Variations of potential air toxics from the top to the bottom of a set of bench samples from the Pittsburgh coal bed in Ohio. (Values are in parts-per-million on a whole coal basis. Total thickness of the bed is 52.5 inches.)

Samples	top	2	3	4	5	6	bottom
	1						7
<u>Element</u>							
Antimony	0.6	0.2	0.2	0.2	0.3	0.3	0.4
Arsenic	10.4	12.6	4.9	6.3	8.2	31.9	12.8
Beryllium	3.0	1.5	0.8	0.7	1.6	1.3	3.4
Cadmium	0.10	0.09	0.03	0.05	0.08	0.08	0.09
Chromium	30.4	7.4	6.9	9.8	32.7	11.8	12.5
Cobalt	9.2	2.2	1.6	2.1	6.6	1.3	3.3
Lead	8.7	1.6	1.3	1.4	5.5	1.5	5.1
Manganese	12.6	10.3	8.8	7.34	24.8	8.4	13.7
Mercury	0.24	0.29	0.10	0.14	0.20	0.19	0.05
Nickel	16.6	5.8	2.9	4.7	21.3	5.9	13.7
Selenium	8.5	3.3	1.1	1.5	2.2	0.9	0.9
Uranium	2.0	0.3	0.3	0.4	1.3	0.3	0.6

quality data base was designed to assess vertical and lateral variation of coal quality parameters and was not designed to determine the amount of a component per ton of coal. Therefore, the data are not weighted by bed thickness or heat value.

#### Modes of Occurrence of Trace Elements

The Coal Quality data base provides information on the concentration and vertical and lateral distribution of many coal quality parameters including the major-, minor-, and trace-elements. This information is especially useful for seeking coals with particular coal quality characteristics or for determining regional trends.

However, to anticipate the environmental impact, technological behavior, or byproduct potential of an element requires information on the element's modes of occurrence (chemical form) and textural relations. Currently, information on modes of occurrence is not included in the coal quality data base. The USGS has, however, conducted extensive investigations on the modes of occurrence and textural relations of the elements in coal. The results of these investigations have been published in numerous papers. See, for example: Zubovic (1966, 1976); Zubovic and others (1960); Finkelman (1981, 1993, in press); Finkelman and others (1990); Palmer and Filby (1983); Ruppert and others (1984).

#### Statistical Correlations of Coal Quality Parameters

One indirect method of deducing an element's mode of occurrence is to determine the correlation of the element with ash

yield, sulfur, or other coal quality parameters. This can be a useful, but it also can be a potentially misleading procedure.

This is because in a geologic data base, such as the USGS's Coal Quality data base, correlation coefficients generally reflect a common source rather than a close chemical or physical affinity. For example, Cecil and others (1979) found petrographic evidence of extensive mobilization of many trace elements in the Upper Freeport coal bed. Because the Upper Freeport coal bed was a closed geochemical system for many elements, they retained their statistical correlations with ash yield and other parameters, despite these elements having changed their chemical form and distribution patterns. Finkelman (1981), based on research on the Gulf Coast lignites, also concluded that there was extensive remobilization of the elements despite strong statistical correlations between element concentrations and ash yield.

It is evident that caution must be exercised in interpreting results of statistical tests applied to the Coal Quality data base, or any other geochemical data base. Table 7 contains a list of strengths and potential weaknesses of the Coal Quality data base as well as cautions to those using the data base.

Table 7. Strengths and Weaknesses of the USGS Coal Quality Data Base and Cautions for its Use

STRENGTHS

- \* Large size
  - 13,035 analyzed U.S. samples.
  - All major coal basins and major coal producing beds are represented.
- \* Reliable data
  - High quality analytical procedures used, such as ASTM (1993) standards.
  - State-of-the-art analytical procedures used to generate element analyses.
  - Standardized sample collection and handling procedures.
- \* Comprehensive
  - 136 parameters can be determined on each sample, including data on more than 75 chemical elements.
- \* Convenient
  - Easy public access
  - Multimedia data dissemination
  - Free to inexpensive

Weaknesses

- \* Dated
  - Many samples collected and analyzed prior to 1982.
  - In the immediate vicinity of many samples coal is now mined out or coal mining has ceased.
- \* Not geographically balanced
  - Only 113 samples from Illinois
  - 58 analyses from Idaho
  - No clean coal data
  - No mineralogical data
  - No modes of occurrence information
- \* Data base is incomplete
  - Additional samples required to adequately characterize all major beds in all coal-bearing areas of the country.

### Cautions

- \* Geologic/  
Exploration  
data base
  - Sample collection not geared to production.
  - Some samples have high ash yields or high sulfur contents. Some samples are from coal beds that are too thin or too deep for mining or are from frontier areas.
  - Partings > 10 cm eliminated.
  
- \* Some analytical procedures have changed with time.
  
- \* Samples do not have a uniform geographic distribution within coal basins for individual coal beds. Many samples were collected as opportunities presented, rather than collected as or where needed.
  
- \* Limited statistical evaluation of data.
  
- \* Samples collected by more than 20 different agencies with many individual collectors, not all of whom adhered strictly to the standards prescribed by the USGS.

## Methods of Data Dissemination

Information from the Coal Quality data base can be obtained through several different formats and media. Data requested from the USGS Branch of Coal Geology can be obtained on cartridge tapes, 3.5" or 5.25" floppy disks, or by hardcopy. Output files from searches performed by USGS personnel can also be retrieved by outside users via anonymous file transfer protocol. At present, data can be output from Rbase as ASCII delimited, ASCII fixed, Lotus123 (.wks), Dbase (.dbf), DIF, and Multiplan (SLYK) files. The chemical data are stored on a CD-ROM (currently in a test mode: projected date of availability to the public is July 1994) and can be accessed via an accompanying search and retrieval program called GSSEARCH. Output files from the CD-ROM can be exported in formats usable in PC-based data base managers or spreadsheets. The data base should be available sometime in 1994 for searches on the NCRDS's SUN UNIX server via Internet using the INGRES relational data base manager.

Requests for information should reference the Freedom of Information Act and can be mailed or faxed to the Branch of Coal Geology. The mailing address is: U. S. Geological Survey, Attention: Linda Bragg, Mail Stop 956 National Center, Reston, VA 22092. The fax number is 703-648-6419. Phone requests should be followed by written requests. When more than one hour is required to complete a data search, costs to cover materials and the hourly wages of the employee will be charged.

The following persons should be able to provide assistance with data requests and interpretation of the resulting informa-

tion:

Linda Bragg	703-648-6451
Robert Finkelman	703-648-6412
Charles Oman	703-648-6452
Susan Tewalt	703-648-6437

## References

- ASTM (American Society for Testing and Materials), 1993, Annual book of ASTM standards, Volume 05.05 Gaseous fuels; coal and coke: ASTM, Philadelphia, 526 p.
- Barnes, F. F., 1961, Coal fields of the United States -- Sheet 2, Alaska: U.S. Geological Survey, scale 1:5,000,000.
- Cargill, S. M., Olson, A. C., Medlin, A. L., and Carter, M. D., 1976, PACER - Data entry, retrieval, and update for the National Coal Resources Data System (Phase I): U.S. Geological Survey Professional Paper 978, 107 p.
- Cecil, C. B., Stanton, R. W., Allshouse, S. D., and Finkelman, 1979, Interbed variation in and geologic controls on element concentrations in the Upper Freeport coal: American Chemical Society, Fuel Chemistry Division, Chemical Congress Abstract no. 48.
- Finkelman, A. C., Wong, C.-J. J., Cheng, A. C., and Finkelman, R. B., 1991, Bibliography of publications containing major, minor, and trace element data from the National Coal Resources Data System: U.S. Geological Survey Open-File Report 91-123, 19 p.
- Finkelman, R. B., 1981, Modes of occurrence of trace elements in coal: U. S. Geological Survey Open-File Report 81-99, 312 p.
- Finkelman, R. B., 1993, Trace and minor elements in coal. In Organic geochemistry: principles and applications, M. H. Engel and S. A. Macko, editors: Plenum Publishing Corp.,

New York, p. 593-607.

Finkelman, R. B., in press, Modes of occurrence of hazardous elements in coal: level of confidence: Fuel Processing Technology.

Finkelman, R. B., Palmer, C. A., Krasnow, M. R., Aruscavage, P. S., and Sellers, G. A., 1990, Heating and leaching behavior of elements in the eight Argonne Premium Coal Samples: Energy and Fuels, v. 4, no. 6, p. 755-767.

Golightly, D. W., and Simon, F. O., 1989, Methods for sampling and inorganic analysis of coal: U. S. Geological Survey Bulletin 1823, 72 p.

Palmer, C. A., and Filby, R. H., 1983, Determination of mode of occurrence of trace elements in the Upper Freeport coal bed using size and density separation procedures: Proceedings, 1983 International Conference on Coal Science, International Energy Agency, p. 365-368.

Ruppert, L. F., Cecil, C. B., and Stanton, R. W., 1984, The origin of quartz in coal: American Chemical Society Division of Fuel Chemistry, Preprints, p. 14-20.

Stanton, R. W., 1989, Sampling of coal beds for analysis. In Methods for sampling and inorganic analysis of coal, D.W. Golightly and F. O. Simon, editors: U.S. Geological Survey Bulletin 1823, p. 7-13.

Swanson, V. E., and Huffman, Claude, Jr., 1976, Guidelines for sample collecting and analytical methods used in the U. S. Geological Survey for determining chemical composition of coal: U. S. Geological Survey Circular 735, 11 p.

Trumbull, J. V. A., 1960, Coal fields of the United States --

Sheet 1: U. S. Geological Survey, scale 1:5,000,000.

U. S. Statues at Large, 1990, Public Law 101-549. Provisions for attainment and maintenance of national ambient air quality standards. 101st Congress, 2nd Session, v. 104, part 4, p. 2353-3358.

Zubovic, P., 1966, Physicochemical properties of certain minor elements as controlling factors in their distribution in coal. In Coal Science, R. F. Gould, editor: Americal Chemical Society, Washington, D. C. Advances in Chemistry, no. 55, p. 221-246.

Zubovic, P. 1976, Geochemistry of trace elements in coal. In Symposium Proceedings: Environmental aspects of fuel conversion technology II, F. A. Ayer, compiler: U.S. Environmental Protection Agency, Technology Series EPA-600/2-76-149, p. 47-63.

Zubovic, P., Stadnichenko, T., and Sheffey, N. B., 1960, The association of minor elements with organic and inorganic phases of coal: U.S. Geological Suevey Professional Paper 400-B, p. B84-B87..pa

## **APPENDIX**

Definitions of parameters in the  
U.S. Geological Survey Coal Quality data base.

U.S. GEOLOGICAL SURVEY OPEN-FILE REPORT 94-205

U.S. GEOLOGICAL SURVEY  
COAL QUALITY (COALQUAL) DATABASE: VERSION 1.3

The COALQUAL database, a subset of the 13,035 samples contained in the NCRDS' (National Coal Resources Data System) USCHEM (US geoCHEMical) data base, contains coal quality data in which a complete record represents a coal sample with a possible total of 136 fields. Chemical data for the samples are presented in this data base on an AS-RECEIVED, WHOLE-COAL basis. In addition, the oxides are also shown as a percentage of the total ash on an ash basis. Some fields may not contain data and will be represented as NO DATA ENTERED in the text fields or NULL values in the numeric fields. In the .dbf file (dBase data file) on the CD-ROM, NULL values will be represented as negative zeros in the numeric fields. The files displayed on the screen or produced as output files by GSSEARCH will contain blanks in fields having no data.

Details of sampling methods and analytical procedures can be obtained from the cited references and are contained as viewable documents on this CD-ROM. These ASCII files can be printed to dot matrix or laser printers.

The following section provides a description of each data field in the COALQUAL database and an explanation of all codes that are used. The analytical method(s) is noted for each field of coal quality data.

The following list contains the number of significant figures for analytical methods, when known. The user is cautioned to utilize only the correct number of significant figures as noted below for any final results of calculations or summaries of values in the database. For American Society for Testing and Materials (ASTM) analytical methods (ASTM Annual Book of Standards, 1992) we list the precision differences for reproducibility, in lieu of the known number of significant figures. All ASTM data are reported to two decimal places unless otherwise noted.

ASTM Property	Comments
Gross Calorific Value	100 Btu/lb on a DRY basis (reported with no decimal places)
Proximate Analysis	
Moisture	0.3 percent for <5 percent moisture; 0.5 percent for > 5 percent moisture
Ash yield	0.3 percent no carbonates present 0.5 percent carbonates present; 1.0 percent coals with > 12 percent ash containing carbonates and pyrite
Volatile matter [based on rank]	anthracite 0.6 percent; semianthracite and bituminous 1.0 percent;

Fixed carbon	subbituminous 1.4 percent; lignite and peat 2.0 percent calculated by difference {100-volatile matter (dry, ash-free basis)}
Ultimate Analysis	
Total Sulfur	0.1 percent for <2 percent sulfur; 0.2 percent for > 2 percent sulfur; 0.05 percent for coke
Carbon	0.3 percent
Hydrogen	0.07 percent
Nitrogen	not yet available
Forms of sulfur	
Sulfate	0.04 percent by weight
Pyritic sulfur	95 percent confidence interval of multiple analyses
Organic sulfur	calculated by difference {total sulfur-pyritic sulfur-sulfate sulfur}
Grindability of coal by Hardgrove-Machine (Reported to 1 decimal place)	3 points
Ash Fusion temperatures	Normally reported to the nearest 10 degrees Fahrenheit

THE USGS MAKES NO CLAIMS AS TO THE ACCURACY OF COAL RANK CALCULATED FROM PARAMETERS OF PROXIMATE AND ULTIMATE ANALYSES. CALCULATED RANK MAY BE HIGHER FOR SOME SAMPLES DUE TO AIR-DRYING OF SAMPLES BEFORE ANALYSES.

-----  
-----

USGS ANALYTICAL METHODS SIGNIFICANT FIGURES: ALL USGS ANALYTICAL DATA ARE REPORTED TO TWO SIGNIFICANT FIGURES, EXCEPT FOR GSASH WHICH IS REPORTED TO 1 DECIMAL PLACE. ALL ELEMENTAL DATA ARE REPORTED IN PARTS-PER-MILLION (PPM). DATA FIELDS ARE LABELED BY THE TWO LETTER SYMBOL FOR THE ELEMENT AND HAVE A SUFFIX OF E SUCH AS AS E, WHICH REPRESENTS ELEMENTAL ARSENIC. SEE THE FOLLOWING TABLE FOR THE DEFINITIONS OF OTHER FIELDS IN THE DATA BASE AND THE MANNER IN WHICH THE DATA ARE REPORTED.

Query operations may be performed on nearly all fields; all significant fields have been indexed for GSSEARCH.

Qualified data are not included in the data base as published. Greater than values have been treated as the value. Less than values have been treated by multiplying the value by 0.7 (SEE CONNOR, 1976 in REFERENC.DOC) and dropping the qualifier. NULL values represent zero values which were qualified. Qualified zero values are obtained when a sample was not analyzed for an element, when the element had interference in its analysis, and when an element was not detected during an analysis. The percentage of qualified values for each element was calculated using the original as-received data base (USCHEM).

This percentage calculation did not include qualifiers which resulted in NULL values. See each element in TECHINFO.DOC or in the HELP files.

Data for elements having more than 25 percent qualified values (Au, Bi, Cd, Cl, Dy, Er, Gd, Ge, Ho, In, Ir, Nd, Os, Pd, Pr, Pt, Rb, Re, Rh, Ru, Sn, Te, Tl, and Tm) should not be used and elements with 10 to 25 percent qualified values should be used with EXTREME caution.

Column definitions

# Name	##Type	### Definition
#		COLUMN INDICATES ITEM NUMBER IN DATA BASE AND NAME
##		COLUMN INDICATES TYPE OF DATA FIELD: TEXT IS A CHARACTER FIELD INTEGER IS AN INTEGER NUMERIC FIELD REAL IS A REAL NUMBER FIELD
###		COLUMN INDICATES TEXT FIELD LENGTH
1	LABID TEXT	1 Analysis Identification Number (Alphabetic)
2	SAMPLENO TEXT Note:	6 Analysis Identification Number (Alphabetic) The combination of LABID and SAMPLENO form a unique sample identification number
3	STATE TEXT	30 Name of State where sample was collected
4	COUNTY TEXT	30 Name of county in state (or borough name in Alaska) where sample was collected
5	LATITUDE INTEGER	Latitude coordinate for point source location of coal sample (degrees, minutes, and decimal seconds)
6	NS TEXT	1 Hemisphere of Latitude (N OR S)
7	LONGITUD INTEGER	Longitude coordinate for point source location of coal sample (degrees, minutes, and decimal seconds)
8	EW TEXT	1 Hemisphere of Longitude (E OR W)
9	CPROVINC TEXT	40 Coal Province Name--See Wood and others (1983), US Geological Survey Circular 891, page 16
10	CREGION TEXT	48 Coal Region Name--See Wood and others (1983), US Geological Survey Circular 891, page 15
11	CFIELD TEXT	40 Coal Field Name--See Barnes, F. F., 1961, Coal fields of the United States--Sheet 2, Alaska: U.S. Geological Survey, scale 1:5,000,000 See Trumball, J. V. A., 1960, Coal fields of the United States--Sheet 1: U.S. Geological Survey, scale 1:5,000,000
12	DISTRICT TEXT	48 District Name--Depending on the state, this field

may be mining districts, political divisions (such as townships or boroughs), or other subdivisions of the state

13	CFORMATN	TEXT	40	Formation Name--Stratigraphic formation name specified by the collector of the sample, usually a state geologist; or if collected by USGS personnel (SEE Stratigraphic Nomenclature Databases for the United States, its possessions and territories)
14	CGROUP	TEXT	40	Group Name--Stratigraphic group name specified by the collector of the sample, usually a state geologist; or if collected by USGS personnel (SEE Stratigraphic Nomenclature Databases for the United States, its possessions and territories)
15	CBED	TEXT	40	Bed Name--Stratigraphic bed name specified by the collector of the sample, usually a state geologist; or if collected by USGS personnel (SEE Stratigraphic Nomenclature Databases for the United States, its possessions and territories)
16	CMEMBER	TEXT	40	Member Name--Stratigraphic member name specified by the collector of the sample, usually a state geologist; or if collected by USGS personnel (SEE Stratigraphic Nomenclature Databases for the United States, its possessions and territories)
17	CZONE	TEXT	40	Relationship between non-coal material and the coal bed (e.g., parting, roof, floor--not a coal zone name)
18	DEPTH	REAL		Depth from the surface of the earth to the top of the sample if the sample is part of a drill core. If samples are not drill cores, but samples are benched, then depth is a measure from the top of the uppermost bench to the top of the next sample in the benched series. (Depth is measured in inches)
19	SAMPTHK	REAL		Thickness of the sample, measured in inches
20	SYSTEM	TEXT	40	System designates a fundamental unit of the sample's geologic age (SEE Stratigraphic Nomenclature Databases for the United States, its possessions and territories)
21	SER_EPOC	TEXT	40	Designates a fundamental unit of the sample's geologic age, either series or epoch (SEE Stratigraphic Nomenclature Databases for the United States, its possessions and territories)
22	COMMENTS	TEXT	100	Used as a comment field to describe the mine name,

the drill hole identified, or other miscellaneous information about the sample

23	MAP	TEXT	40	Usually the topographic quadrangle map name and series. For some areas of the U.S. where there are no topographic maps, another type of map name may be used along with the scale of the map.
24	COLLECTR	TEXT	60	The agency and name of the person collecting or submitting the sample
25	POINTID	TEXT	160	The field number assigned by the collector or submitter of the sample. For composited samples, pointid contains a list of the LABID and SAMPLENO for all samples combined.
26	SUBDATE	DATE		The date the sample was confirmed by the USGS analytical labs as having been submitted for analysis (methods of analyses are determined by this date). (MM/DD/YY)
27	ESTRANK	TEXT	30	Estimated rank of coal (also includes lithology for coal-related rock samples, which are not included in the database and are not listed here). --See Barnes, F. F., 1961, Coal fields of the United States--Sheet 2, Alaska: U.S. Geological Survey Map, scale 1:5,000,000 --See Trumball, J. V. A., 1960, Coal fields of the United States--Sheet 1: U.S. Geological Survey Map, scale 1:5,000,000 Note: THE USGS MAKES NO CLAIMS AS TO THE ACCURACY OF COAL RANK CALCULATED FROM PARAMETERS OF PROXIMATE AND ULTIMATE ANALYSES. WITH SOME SAMPLES CALCULATED RANK MAY BE HIGHER DUE TO AIR-DRYING OF SAMPLES BEFORE ANALYSES. ANTHRACITE SEMI-ANTHRACITE BITUMINOUS SUBBITUMINOUS LIGNITE COAL
28	LABCODE	INTEGER		Code for laboratory performing analyses 5 = U.S. Geological Survey (USGS) 15 = USBM and USGS 35 = State agency and USGS 65 = USGS and Geochemical Testing Co., Somerset, PA 75 = USGS and Dickinson Laboratories, Inc., El Paso, TX 765 = USGS, Dickinson Laboratories, Inc., and Geochemical Testing Co.
29	SAMPTYPE	INTEGER		Sample type

1 = Channel  
3 = Drill core  
11 = Weathered channel

30 ANALTYPE INTEGER Analysis type  
1 = As-received

31 VALREP INTEGER Values represent  
1 = Single Sample (Most common)  
2 = Average of more than one sample (composite)  
NOTE: A composite sample may be made by either  
A) physically combining samples on the basis of their thicknesses  
B) or, mathematically weighting data from individual samples on the basis of bed thickness.  
4 = Composite samples for ASTM analyses and samples for individual USGS analyses  
5 = Composite samples for USGS analyses and individual samples for ASTM analyses  
20 = Upper split (incremental sample, not a bench)  
21 = Lower split (incremental sample, not a bench)  
22 = Middle split (incremental sample, not a bench)  
DEFINITIONS:  
A) Splits = Herein defined as incremental samples of beds separated by 1 foot or more of non-coal material

32 BTU REAL Gross calorific value of the coal sample expressed in British Thermal Units (BTU/lb) as determined by ASTM method D-2015. There are no qualified non-zero values for BTU in USCHEM.

33 ASHDEF REAL Ash Deformation temperature in degrees Fahrenheit as determined by ASTM method D1857 in reducing atmosphere. Approximately 12 percent of the non-zero values for ASHDEF in USCHEM are qualified.

34 ASHSOF REAL Ash Softening temperature in degrees Fahrenheit as determined by ASTM method D1857 in reducing atmosphere. Approximately 19 percent of the non-zero values for ASHSOF in USCHEM are qualified.

35 ASHFLD REAL Ash Fluid temperature in degrees Fahrenheit as determined by ASTM method D1857- in reducing atmosphere. Approximately 23 percent of the non-zero values for ASHFLD in USCHEM are qualified.

36 FRESWL REAL Free-Swelling index as determined by ASTM method D-720. There are no qualified non-zero values for FRESWL in USCHEM.

37 MOISTR REAL Moisture value (as-received basis) in percent as determined by ASTM method D-3173. There are no

qualified non-zero values for MOISTR in USCHEM.

38	VOLMAT	REAL	Volatile matter value in percent as determined by ASTM method D-3175. There are no qualified non-zero values for VOLMAT in USCHEM.
39	FIXEDC	REAL	Fixed Carbon value in percent as determined by ASTM method D-3172. There are no qualified non-zero values for FIXEDC in USCHEM.
40	STDASH	REAL	Ash value in percent as determined by ASTM method D-3174 (ash obtained at 750 degrees C). There are no qualified non-zero values for STDASH in USCHEM.
41	HYDRGN	REAL	Hydrogen value in percent as determined by ASTM method D-3178. There are no qualified non-zero values for HYDRGN in USCHEM.
42	CARBON	REAL	Carbon value in percent as determined by ASTM method D-3178 in USGS or other labs (see LABCODE). There is one qualified non-zero value for CARBON in USCHEM.
43	NITRGN	REAL	Nitrogen value in percent as determined by ASTM method D-3179. There are no qualified non-zero values for NITRGN in USCHEM.
44	OXYGEN	REAL	Oxygen value in percent as determined by ASTM method D-3176. There are no qualified non-zero values for OXYGEN in USCHEM.
45	SULFUR	REAL	Sulfur value in percent as determined by ASTM method D-3177 in USGS or other labs (see LABCODE). Less than 1 percent of the non-zero values for SULFUR in USCHEM are qualified.
46	SLFATE	REAL	Sulfate value in percent as determined by ASTM method D-2492 in other labs or similar method in USGS labs (see LABCODE). Approximately 22 percent of the non-zero values for SLFATE in USCHEM are qualified.
47	SLFPYR	REAL	Pyritic Sulfur value in percent as determined by ASTM method D-2492 in other labs or similar method in USGS labs (see LABCODE). Approximately 17 percent of the non-zero values for SLFPYR in USCHEM are qualified.
48	SLFORG	REAL	Organic Sulfur value in percent as determined by ASTM method D-2492 in USGS or other labs (see LABCODE). Approximately 18 percent of the non-zero values for SLFORG in USCHEM are qualified.
49	ADLOSS	REAL	Air-Dried loss value in percent as determined by

ASTM method D-2013. Less than 1 percent of the non-zero values for ADLOSS in USCHEM are qualified.

- 50 HGI REAL Hardgrove Grindability value as determined by ASTM method D-409. There are no qualified non-zero values for HGI in USCHEM.
- 51 EQMOIS REAL Equilibrium moisture value in percent as determined by ASTM method D-1412. There are no qualified non-zero values for EQMOIS in USCHEM.
- 52 GSASH REAL Ash value in percent as determined by USGS laboratories (ash obtained at 525 degrees C). There is one qualified non-zero value for GSASH in USCHEM.
- 53 SIO2 REAL Silicon dioxide (SIO2) value in percent as determined on the coal ash by USGS laboratories using X-ray fluorescence analysis (ash obtained at 525 degrees C)--May be converted from SI\_E value in parts-per-million which was determined by the same method. There are no qualified non-zero values for SIO2 in USCHEM.
- 54 AL2O3 REAL Aluminum oxide (AL2O3) value in percent as determined on the coal ash by USGS laboratories using X-ray fluorescence analysis (ash obtained at 525 degrees C)--May be converted from AL\_E value in parts-per-million which was determined by the same method. There are no qualified non-zero values for AL2O3 in USCHEM.
- 55 CAO REAL Calcium oxide (CAO) value in percent as determined on the coal ash by USGS laboratories using X-ray fluorescence analysis (ash obtained at 525 degrees C)--May be converted from CA\_E value in parts-per-million which was determined by the same method. There are no qualified non-zero values for CAO in USCHEM.
- 56 MGO REAL Magnesium oxide (MGO) value in percent as determined on the coal ash by USGS laboratories using wet chemistry analysis (atomic absorption: ash obtained at 525 degrees C)--May be converted from MG\_E value in parts-per-million or percent which was determined by the same method. Less than 1 percent of the non-zero values for MGO in USCHEM are qualified.
- 57 MNO REAL Manganese oxide (MNO) value in percent. Converted from MN\_E as determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission

spectrographic analysis (ash obtained at 525 degrees C) and later using wet chemistry analysis on the ash to analyze for Mn. Less than 1 percent of the non-zero values for MNO in USCHEM are qualified.

- 58 NA20 REAL Sodium oxide (NA20) value in percent as determined on the coal ash by USGS laboratories using wet chemistry analysis (atomic absorption: ash obtained at 525 degrees C)--May be converted from NA\_E value in parts-per-million or percent which was determined by the same method. Less than 1 percent of the non-zero values for NA20 in USCHEM are qualified.
- 59 K20 REAL Potassium oxide (K20) value in percent as determined on the coal ash by USGS laboratories using X-ray fluorescence analysis (ash obtained at 525 degrees C)--May be converted from K\_E value in parts-per-million which was determined by the same method. Less than 1 percent of the non-zero values for K20 in USCHEM are qualified.
- 60 FE203 REAL Ferric oxide (FE203) value in percent as determined on the coal ash by USGS laboratories using X-ray fluorescence analysis (ash obtained at 525 degrees C)--May be converted from FE\_E value in parts-per-million which was determined by the same method. Less than 1 percent of the non-zero values for FE203 in USCHEM are qualified.
- 61 TIO2 REAL Titanium oxide (TIO2) value in percent as determined on the coal ash by USGS laboratories using X-ray fluorescence analysis (ash obtained at 525 degrees C)--May be converted from TI\_E value in parts-per-million which was determined by the same method. Less than 1 percent of the non-zero values for TIO2 in USCHEM are qualified.
- 62 P205 REAL Phosphorous pentoxide (P205) value in percent as determined on the coal ash by USGS laboratories using X-ray fluorescence analysis (ash obtained at 525 degrees C)--May be converted from P (P\_E) value in parts-per-million which was determined by the same method. Approximately 19 percent of the non-zero values for P205 in USCHEM are qualified.
- 63 SO3 REAL Sulfur trioxide (SO3) value in percent as determined on the coal ash by USGS laboratories using X-ray fluorescence analysis (ash obtained at 525 degrees C)--May be converted from S\_E value in parts-per-million which was determined by the same method. Approximately 1 percent of the non-zero values for SO3 in USCHEM are qualified.

- 64 SI\_E REAL Silicon (SI) value in parts-per-million on whole-coal basis, converted from value as determined on coal ash by USGS laboratories using X-ray fluorescence analysis (ash obtained at 525 degrees C)--May be converted from SIO2 value in percent which was determined by the same method. There are no qualified non-zero values for SI\_E in USCHEM.
- 65 AL\_E REAL Aluminum (AL) value in parts-per-million on whole-coal basis, converted from value as determined on coal ash by USGS laboratories using X-ray fluorescence analysis (ash obtained at 525 degrees C)--May be converted from AL2O3 value in percent which was determined by the same method. There are no qualified non-zero values for AL\_E in USCHEM.
- 66 CA\_E REAL Calcium (CA) value in parts-per-million on whole-coal basis, converted from value as determined on coal ash by USGS laboratories using X-ray fluorescence analysis (ash obtained at 525 degrees C)--May be converted from CAO value in percent which was determined by the same method. There are no qualified non-zero values for CA\_E in USCHEM.
- 67 MG\_E REAL Magnesium (MG) value in parts-per-million on whole-coal basis, converted from value as determined on coal ash by USGS laboratories using wet chemistry analysis (atomic absorption: ash obtained at 525 degrees C)--May be converted from MGO value in percent which was determined by the same method. Less than 1 percent of the non-zero values for MG\_E in USCHEM are qualified.
- 68 NA\_E REAL Sodium (NA) value in parts-per-million on whole-coal basis, converted from value as determined on coal ash by USGS laboratories using wet chemistry analysis (atomic absorption: ash obtained at 525 degrees C)--May be converted from NA2O value in percent which was determined by the same method. Less than 1 percent of the non-zero values for NA\_E in USCHEM are qualified.
- 69 K\_E REAL Potassium (K) value in parts-per-million on whole-coal basis, converted from value as determined on coal ash by USGS laboratories using X-ray fluorescence analysis (ash obtained at 525 degrees C)--May be converted from K2O value in percent which was determined by the same method. Less than 1 percent of the non-zero values for K\_E in USCHEM are qualified.

70 FE\_E REAL Iron (FE) value in parts-per-million on whole-coal basis, converted from value as determined on coal ash by USGS laboratories using X-ray fluorescence analysis (ash obtained at 525 degrees C)--May be converted from FE2O3 value in percent which was determined by the same method. Less than 1 percent of the non-zero values for FE\_E in USCHEM are qualified.

71 TI\_E REAL Titanium (TI) value in parts-per-million on whole-coal basis, converted from value as determined on coal ash by USGS laboratories using X-ray fluorescence analysis (ash obtained at 525 degrees C)--May be converted from TIO2 value in percent which was determined by the same method. Less than 1 percent of the non-zero values for TI\_E in USCHEM are qualified.

72 S\_E REAL Sulfur (S) value in parts-per-million on whole-coal basis, converted from value as determined on coal ash by USGS laboratories using X-ray fluorescence analysis (ash obtained at 525 degrees C)--May be converted from SO3 value in percent which was determined by the same method. Approximately 1 percent of the non-zero values for S\_E in USCHEM are qualified. THIS IS NOT STANDARD ASTM SULFUR.

73 AG\_E REAL Silver (AG) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Approximately 20 percent of the non-zero values for AG\_E in USCHEM are qualified.

74 AS\_E REAL Arsenic (AS) value in parts-per-million as determined on whole-coal by USGS laboratories using either wet chemistry analysis for samples analyzed in Denver (D for LABID) before 1976 or Instrumental Neutron Activation Analysis (INAA) for samples analyzed in Reston (W for LABID) and for samples analyzed after 1976 in Denver. Less than 1 percent of the non-zero values for AS\_E in USCHEM are qualified.

75 AU\_E REAL Gold (AU) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at

525 degrees C). Approximately 100 percent of the non-zero values for AU\_E in USCHEM are qualified.

- 76 B\_E REAL Boron (B) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Approximately 5 percent of the non-zero values for B\_E in USCHEM are qualified.
- 77 BA\_E REAL Barium (BA) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Approximately 0.5 percent of the non-zero values for BA\_E in USCHEM are qualified.
- 78 BE\_E REAL Beryllium (BE) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Approximately 2 percent of the non-zero values for BE\_E in USCHEM are qualified.
- 79 BI\_E REAL Bismuth (BI) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Approximately 98 percent of the non-zero values for BI\_E in USCHEM are qualified.
- 80 BR\_E REAL Bromine (BR) value in parts-per-million as determined on whole-coal by USGS laboratories for samples having a LABID=W using Instrumental Neutron Activation Analysis (INAA). Approximately 7 percent of the non-zero values for BR\_E in USCHEM are qualified.
- 81 CD\_E REAL Cadmium (CD) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using wet chemistry analysis (atomic absorption--ash obtained at 525 degrees C). Approximately 29 percent of the non-zero values for CD\_E in USCHEM are qualified.
- 82 CE\_E REAL Cerium (CE) value in parts-per-million on whole-

coal basis, converted from value determined on coal ash by USGS laboratories using either semi-quantitative 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C) for all samples with LABID = D or all samples with LABID = W and SUBDATE less than or equal to 75/05/27. Samples with LABID = W and SUBDATE greater than 75/05/27 were analyzed on a whole-coal basis using Instrumental Neutron Activation Analysis (INAA). Approximately 10 percent of the non-zero values for CE\_E in USCHEM are qualified.

- 83 CL\_E REAL Chlorine (CL) value in parts-per-million as determined on whole-coal by USGS laboratories using X-ray fluorescence analysis. Approximately 29 percent of the non-zero values for CL\_E in USCHEM are qualified.
- 84 CO\_E REAL Cobalt (CO) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either semi-quantitative 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C) for all samples with LABID = D with SUBDATE less than or equal to 76/08/19 or all samples with LABID = W and SUBDATE less than or equal to 75/05/27. Samples with LABID = W and SUBDATE greater than 75/05/27 or LABID =D and SUBDATE greater than 76/08/19 were analyzed on a whole-coal basis using Instrumental Neutron Activation Analysis (INAA). Approximately 2 percent of the non-zero values for CO\_E in USCHEM are qualified.
- 85 CR\_E REAL Chromium (CR) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either semi-quantitative 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C) for all samples with LABID = D with SUBDATE less than or equal to 76/08/19 or all samples with LABID = W and SUBDATE less than or equal to 75/05/27. Samples with LABID = W and SUBDATE greater than 75/05/27 or LABID =D and SUBDATE greater than 76/08/19 were analyzed on a whole-coal basis using Instrumental Neutron Activation Analysis. Approximately 1 percent of the non-zero values for CR\_E in USCHEM are qualified.

86 CS\_E REAL Cesium (CS) value in parts-per-million on whole coal basis, converted from value determined on coal ash by USGS laboratories using either semi-quantitative 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C) for all samples with LABID = D or all samples with LABID = W and SUBDATE less than or equal to 75/05/27. Samples with LABID = W and SUBDATE greater than 75/05/27 were analyzed on a whole-coal basis using Instrumental Neutron Activation Analysis (INAA). Approximately 8 percent of the non-zero values for CS\_E in USCHEM are qualified.

87 CU\_E REAL Copper (CU) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using wet chemistry analysis (atomic absorption--ash obtained at 525 degrees C). Less than 1 percent of the non-zero values for CU\_E in USCHEM are qualified.

88 DY\_E REAL Dysprosium (DY) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Approximately 89 percent of the non-zero values for DY\_E in USCHEM are qualified.

89 ER\_E REAL Erbium (ER) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Approximately 82 percent of the non-zero values for ER\_E in USCHEM are qualified.

90 EU\_E REAL Europium (EU) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C) for all samples with LABID = D or all samples with LABID = W and SUBDATE less than or equal to 75/05/27. Samples with LABID = W and SUBDATE greater than 75/05/27 were analyzed on a whole-coal basis using Instrumental Neutron Activation Analysis

(INAA). Approximately 6 percent of the non-zero values for EU\_E in USCHEM are qualified.

- 91 F\_E REAL Fluorine (F) value in parts-per-million as determined on whole-coal by USGS laboratories using wet chemistry analysis (ion-selective electrode). Approximately 7 percent of the non-zero values for F\_E in USCHEM are qualified.
- 92 GA\_E REAL Gallium (GA) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Less than 1 percent of the non-zero values for GA\_E in USCHEM are qualified.
- 93 GD\_E REAL Gadolinium (GD) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Approximately 73 percent of the non-zero values for GD\_E in USCHEM are qualified.
- 94 GE\_E REAL Germanium (GE) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Approximately 26 percent of the non-zero values for GE\_E in USCHEM are qualified.
- 95 HF\_E REAL Hafnium (HF) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C) for all samples with LABID = D or all samples with LABID = W and SUBDATE less than or equal to 75/05/27. Samples with LABID = W and SUBDATE greater than 75/05/27 were analyzed on a whole-coal basis using Instrumental Neutron Activation Analysis (INAA). Approximately 10 percent of the non-zero values for HF\_E in USCHEM are qualified.
- 96 HG\_E REAL Mercury (HG) value in parts-per-million as

determined on whole-coal by USGS laboratories using wet chemistry analysis (cold-vapor atomic absorption). Approximately 7 percent of the non-zero values for HG\_E in USCHEM are qualified.

- 97 HO\_E REAL Homium (HO) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Approximately 93 percent of the non-zero values for HO\_E in USCHEM are qualified.
- 98 IN\_E REAL Indium (IN) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Approximately 100 percent of the non-zero values for IN\_E in USCHEM are qualified.
- 99 IR\_E REAL Iridium (IR) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). One hundred percent of the non-zero values for IR\_E in USCHEM are qualified.
- 100 LA\_E REAL Lanthanum (LA) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C) for all samples with LABID = D or all samples with LABID = W and SUBDATE less than or equal to 75/05/27. Samples with LABID = W and SUBDATE greater than 75/05/27 were analyzed on a whole-coal basis using Instrumental Neutron Activation Analysis (INAA). Approximately 10 percent of the non-zero values for LA\_E in USCHEM are qualified.
- 101 LI\_E REAL Lithium (LI) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using wet chemistry analysis (atomic absorption--ash obtained at 525 degrees C). Approximately 1 percent of the non-zero values for LI\_E in USCHEM are qualified.

102 LU\_E REAL Lutetium (LU) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C) for all samples with LABID = D or all samples with LABID = W and SUBDATE less than or equal to 75/05/27. Samples with LABID = W and SUBDATE greater than 75/05/27 were analyzed on a whole-coal basis using Instrumental Neutron Activation Analysis (INAA). Approximately 12 percent of the non-zero values for LU\_E in USCHEM are qualified.

103 MN\_E REAL Manganese (MN) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C) and later using wet chemistry analysis (atomic absorption on the ash). Less than 1 percent of the non-zero values for MN\_E in USCHEM are qualified.

104 MO\_E REAL Molybdenum (MO) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Approximately 7 percent of the non-zero values for MO\_E in USCHEM are qualified.

105 NB\_E REAL Niobium (NB) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Approximately 11 percent of the non-zero values for NB\_E in USCHEM are qualified.

106 ND\_E REAL Neodymium (ND) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Approximately 31 percent of the non-zero values for ND\_E in USCHEM are

qualified.

- 107 NI\_E REAL Nickel (NI) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Approximately 1 percent of the non-zero values for NI\_E in USCHEM are qualified.
- 108 OS\_E REAL Osmium (OS) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Approximately 100 percent of the non-zero values for OS\_E in USCHEM are qualified.
- 109 P\_E REAL Phosphorus (P) value in parts-per-million as determined on the coal ash by USGS laboratories using X-ray fluorescence analysis (ash obtained at 525 degrees C)--May be converted from P205 value in percent which was determined by the same method. Approximately 19 percent of the non-zero values for P\_E in USCHEM are qualified.
- 110 PB\_E REAL Lead (PB) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using wet chemistry analysis (atomic absorption--ash obtained at 525 degrees C). Approximately 9 percent of the non-zero values for PB\_E in USCHEM are qualified.
- 111 PD\_E REAL Palladium (PD) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Approximately 100 percent of the non-zero values for PD\_E in USCHEM are qualified.
- 112 PR\_E REAL Praseodymium (PR) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Approximately 82 percent of the non-zero values for PR\_E in USCHEM are

qualified.

- 113 PT\_E REAL Platinum (PT) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Approximately 100 percent of the non-zero values for PT\_E in USCHEM are qualified.
- 114 RB\_E REAL Rubidium (RB) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C) for all samples with LABID = D or all samples with LABID = W and SUBDATE less than or equal to 75/05/27. Samples with LABID = W and SUBDATE greater than 75/05/27 were analyzed on a whole-coal basis using Instrumental Neutron Activation Analysis (INAA). Approximately 54 percent of the non-zero values for RB\_E in USCHEM are qualified.
- 115 RE\_E REAL Rhenium (RE) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Approximately 100 percent of the non-zero values for RE\_E in USCHEM are qualified.
- 116 RH\_E REAL Rhodium (RH) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Approximately 100 percent of the non-zero values for RH\_E in USCHEM are qualified.
- 117 RU\_E REAL Ruthenium (RU) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Approximately 100 percent of non-zero values for RU\_E in USCHEM are qualified.

- 118 SB\_E REAL Antimony (SB) value in parts-per-million as determined on whole-coal by USGS laboratories using wet chemistry analysis (Rhodamine B) for with LABID = D and SUBDATE less than or equal to 76/08/19. Samples with LABID = D and subdate greater than 76/08/19 and samples with LABID = W were analyzed using Instrumental Neutron Activation Analysis (INAA). Approximately 5 percent of the non-zero values for SB\_E in USCHEM are qualified.
- 119 SC\_E REAL Scandium (SC) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C) for all samples with LABID = D or all samples with LABID = W and SUBDATE less than or equal to 75/05/27. Samples with LABID = W and SUBDATE greater than 75/05/27 were analyzed on a whole-coal basis using Instrumental Neutron Activation Analysis (INAA). Approximately 1 percent of the non-zero values for SC\_E in USCHEM are qualified.
- 120 SE\_E REAL Selenium (SE) value in parts-per-million as determined on whole-coal basis by USGS laboratories using Xray-fluorescence on all older samples with LABID = D and SUBDATE less than or equal to 78/01/05 and all samples with LABID = W and SUBDATE less than or equal to 75/06/01. Samples with LABID = D and SUBDATE greater than 78/01/05 and all samples with LABID = W and SUBDATE greater than 75/06/01 were analyzed on a whole-coal basis using Instrumental Neutron Activation Analysis (INAA). Approximately 6 percent of the non-zero values for SE\_E in USCHEM are qualified.
- 121 SM\_E REAL Samarium (SM) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C) for all samples with LABID = D or all samples with LABID = W and SUBDATE less than or equal to 75/07/01. Samples with LABID = W and SUBDATE greater than 75/07/01 were analyzed on a whole-coal basis using Instrumental Neutron Activation Analysis (INAA). Approximately 8 percent of the non-zero values for SM\_E in USCHEM are qualified.

122 SN\_E REAL Tin (SN) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Approximately 50 percent of the non-zero values for SN\_E in USCHEM are qualified.

123 SR\_E REAL Strontium (SR) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Less than 1 percent of the non-zero values for SR\_E in USCHEM are qualified.

124 TA\_E REAL Tantalum (TA) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C) for all samples with LABID = D. Samples with LABID = W were analyzed on a whole-coal basis using Instrumental Neutron Activation Analysis (INAA). Approximately 18 percent of the non-zero values for TA\_E in USCHEM are qualified.

125 TB\_E REAL Terbium (TB) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C) for all samples with LABID = D or all samples with LABID = W and SUBDATE less than or equal to 75/05/27. Samples with LABID = W and SUBDATE greater than 75/05/27 were analyzed on a whole-coal basis using Instrumental Neutron Activation Analysis (INAA). Approximately 12 percent of the non-zero values for TB\_E in USCHEM are qualified.

126 TE\_E REAL Tellurium (TE) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash

obtained at 525 degrees C). Approximately 99 percent of the non-zero values for TE\_E in USCHEM are qualified.

- 127 TH\_E REAL Thorium (TH) value in parts-per-million as determined on whole-coal basis by USGS laboratories using Delayed Neutron Analysis (DNA) for older samples and Instrumental Neutron Activation analysis (INAA). Approximately 2 percent of the non-zero values for TH\_E in USCHEM are qualified.
- 128 TL\_E REAL Thallium (TA) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Approximately 95 percent of the non-zero values for TL\_E in USCHEM are qualified.
- 129 TM\_E REAL Thulium (TM) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Approximately 99 percent of the non-zero values for TM\_E in USCHEM are qualified.
- 130 U\_E REAL Uranium (U) value in parts-per-million as determined on whole-coal basis by USGS laboratories using Delayed Neutron Analysis (DNA). Approximately 6 percent of the non-zero values for U\_E in USCHEM are qualified.
- 131 V\_E REAL Vanadium (V) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Less than 1 percent of the non-zero values for V\_E in USCHEM are qualified.
- 132 W\_E REAL Tungsten (W) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C) for all samples with LABID = D. Samples with LABID = W were analyzed

on a whole-coal basis using Instrumental Neutron Activation Analysis (INAA). Approximately 21 percent of the non-zero values for W\_E in USCHEM are qualified.

- 133 Y\_E REAL Yttrium (Y) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Approximately 1 percent of the non-zero values for Y\_E in USCHEM are qualified.
- 134 YB\_E REAL Ytterbium (YB) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C) for all samples with LABID = D or all samples with LABID = W and SUBDATE less than or equal to 75/05/27. Samples with LABID = W and SUBDATE greater than 75/05/27 were analyzed on a whole-coal basis using Instrumental Neutron Activation Analysis (INAA). Approximately 2 percent of the non-zero values for YB\_E in USCHEM are qualified.
- 135 ZN\_E REAL Zinc (ZN) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using wet chemistry analysis (atomic absorption--ash obtained at 525 degrees C). Less than 1 percent of the non-zero values for ZN\_E in USCHEM are qualified.
- 136 ZR\_E REAL Zirconium (ZR) value in parts-per-million on whole-coal basis, converted from value determined on coal ash by USGS laboratories using either 6-Step emission spectrographic analysis for older samples or automatic plate reading computer-assisted emission spectrographic analysis (ash obtained at 525 degrees C). Less than 1 percent of the non-zero values for ZR\_E in USCHEM are qualified.

\*\*\*

End of text; press the Escape key to continue.